

# Paints and varnishes — Coating materials and coating systems for exterior wood

## Part 6: Exposure of wood coatings to artificial weathering using fluorescent UV lamps and water

ICS 87.040

## National foreword

This British Standard is the UK implementation of .

The UK participation in its preparation was entrusted to Technical Committee STI/28, Paint systems for non-metallic substrates.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 October 2008

© BSI 2008

ISBN 978 0 580 55269 4

### Amendments/corrigenda issued since publication

Date	Comments

EUROPEAN STANDARD  
 NORME EUROPÉENNE  
 EUROPÄISCHE NORM

**EN 927-6**

August 2006

ICS 87.040

English Version

**Paints and varnishes - Coating materials and coating systems  
 for exterior wood - Part 6: Exposure of wood coatings to artificial  
 weathering using fluorescent UV lamps and water**

Peintures et vernis - Produits de peinture et systèmes de  
 peinture pour bois en extérieur - Partie 6 : Vieillessement  
 artificiel des revêtements pour bois par exposition à des  
 lampes UV fluorescentes et à de l'eau

Beschichtungsstoffe - Beschichtungsstoffe und  
 Beschichtungssysteme für Holz im Außenbereich - Teil 6:  
 Künstliche Bewitterung von Holzbeschichtungen mit  
 fluoreszierenden UV-Lampen und Wasser

This European Standard was approved by CEN on 26 June 2006.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
 COMITÉ EUROPÉEN DE NORMALISATION  
 EUROPÄISCHES KOMITEE FÜR NORMUNG

**Management Centre: rue de Stassart, 36 B-1050 Brussels**

## Contents

	Page
Foreword.....	3
Introduction .....	4
1 Scope .....	5
2 Normative references .....	5
3 Principle.....	5
4 Apparatus .....	6
4.1 Test chamber.....	6
4.2 Lamps .....	6
4.3 Device for wetting the test panels.....	6
4.4 Black panel thermometer .....	7
4.5 Irradiance control.....	7
5 Test panels .....	7
5.1 Wood .....	7
5.2 Preparation and selection of wood panels .....	8
5.3 Preparation of coated panels .....	8
6 Procedure .....	9
6.1 Examination before exposure .....	9
6.2 Mounting the test panels .....	9
6.3 Exposure.....	9
6.4 Examination of test panels .....	10
7 Precision.....	11
8 Expression of results and test report.....	11
Annex A (normative) Details of test methods.....	12
A.1 Gloss and change of gloss .....	12
A.2 Colour and colour change .....	12
A.3 Blistering .....	12
A.4 Flaking .....	12
A.5 Cracking.....	12
A.6 Chalking.....	12
A.7 General appearance .....	13
A.8 Adhesion.....	13
A.8.1 General.....	13
A.8.2 Apparatus and material .....	13
A.8.3 Procedure .....	13
Annex B (informative) Explanatory notes .....	14
B.1 Explanation of exposure cycle .....	14
B.2 Reproducibility.....	14
B.3 Correlation to natural weathering .....	14
B.4 Dependency on wood species and substrate.....	14
B.5 Recommendation of periodical performance assessments .....	14
Annex C (informative) Test for heartwood in pine .....	15
Annex D (informative) Water treatment, devices for water purification.....	16
Annex E (normative) Test for abnormally porous wood.....	17
Annex F (informative) Alternative procedure for preparation and coating of panels .....	18
Bibliography .....	19

## Foreword

This document (EN 927-6:2006) has been prepared by Technical Committee CEN/TC 139 "Paints and varnishes", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by February 2007, and conflicting national standards shall be withdrawn at the latest by February 2007.

EN 927 consists of the following parts under the general title "*Paints and varnishes — Coating materials and coating systems for exterior wood*":

- *Part 1: Classification and selection;*
- *Part 2: Performance specification;*
- *Part 3: Natural weathering test;*
- *Part 5: Assessment of the liquid water permeability;*
- *Part 6: Exposure of wood coatings to artificial weathering using fluorescent UV lamps and water.*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

## **Introduction**

Coatings from paints, varnishes and similar materials are weathered in a laboratory in order to simulate ageing processes which occur from natural weathering. Generally, a valid correlation between ageing during artificial and natural weathering cannot be expected due to a large number of influencing factors. Certain relationships can only be expected if the effect of the important parameters (spectral distribution of the irradiance in the photochemically relevant range, temperature of the specimen, type of wetting, wetting cycle relative humidity) on the coating is known. However, unlike natural weathering, testing in the laboratory is carried out taking into consideration a limited number of variables which can be controlled and therefore the results are more reproducible.

## 1 Scope

This part of EN 927 specifies a method for determining the resistance of wood coatings to artificial weathering performed in an apparatus equipped with fluorescent UV lamps, condensation and water spray devices.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 927-1, *Paints and varnishes — Coating materials and coating systems for exterior wood — Part 1: Classification and selection*

EN ISO 2409, *Paints and varnishes — Cross-cut test (ISO 2409:1992)*

EN ISO 2808, *Paints and varnishes — Determination of film thickness (ISO 2808:1997)*

EN ISO 2813, *Paints and varnishes — Determination of specular gloss of non-metallic paint films at 20°, 60° and 85° (ISO 2813:1994, including Technical Corrigendum 1:1997)*

EN ISO 4628-1:2003, *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance — Part 1: General introduction and designation system (ISO 4628-1:2003)*

EN ISO 4628-2, *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance — Part 2: Assessment of degree of blistering (ISO 4628-2:2003)*

EN ISO 4628-4, *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance — Part 4: Assessment of degree of cracking (ISO 4628-4:2003)*

EN ISO 4628-5, *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance — Part 5: Assessment of degree of flaking (ISO 4628-5:2003)*

EN ISO 4628-6, *Paints and varnishes — Evaluation of degradation of paint coatings — Designation of intensity, quantity and size of common types of defect - Part 6: Rating of degree of chalking by tape method (ISO 4628-6:1990)*

prEN ISO 11507:2005, *Paints and varnishes — Exposure of coatings to artificial weathering — Exposure to fluorescent UV and water (ISO/DIS 11507:2005)*

ISO 554, *Standard atmospheres for conditioning and/or testing — Specifications*

ISO 7724-1, *Paints and varnishes — Colorimetry — Part 1: Principles*

ISO 7724-2, *Paints and varnishes — Colorimetry — Part 2: Colour measurement*

## 3 Principle

Artificial weathering of coatings using fluorescent UV lamps, condensation or water spray is carried out in order to produce a certain radiant exposure or mutually agreed total number of operation hours, based on a given degree of a change in a property or properties. The properties of the exposed coatings are compared with those of unexposed coatings, which are prepared from the same coating materials under identical conditions or with coatings whose degradation properties are known.

Radiation, temperature and humidity all contribute to the ageing process. Therefore, the apparatus specified in this standard simulates all three factors.

The results obtained by this method do not necessarily directly relate to the results obtained under natural exposure conditions. The relationship between these results needs to be established before the method can be used to predict performance.

The standard test substrate is pine sapwood with the back side of panels coated. However, supplementary information on coating performance may be obtained by conducting optional tests on additional wood species, on pine, modified or impregnated by industrial processes or without coating the back side of the panels.

## 4 Apparatus

### 4.1 Test chamber

The test chamber consists of an enclosure made from corrosion-resistant material which houses the lamps, a heated water tray, spray nozzles and test panel racks.

### 4.2 Lamps

A UV lamp emits UV light from a low pressure mercury arc. The required spectral distribution is achieved by careful selection of the type of phosphor coating on the inner surface of the lamp and the nature of the glass used in the construction of the tubes.

The lamp shall be of the following type:

Lamp, commonly called UV-A 340, with a peak emission at 340 nm and the following relative spectral irradiance (see prEN ISO 11507:2005, lamp type 2):

**Table 1 — Relative spectral irradiance of lamp**

Wavelength nm	Relative spectral irradiance <sup>a</sup> %
$290 < \lambda \leq 400$	100
$\lambda \leq 290$	0,0
$290 < \lambda \leq 300$	0,2
Note: Broader band pass below	
$300 < \lambda \leq 320$	6,2 to 8,6
$320 < \lambda \leq 340$	27,1 to 30,7
$340 < \lambda \leq 360$	34,2 to 35,4
$360 < \lambda \leq 380$	19,5 to 23,7
$380 < \lambda \leq 400$	6,6 to 7,8

<sup>a</sup> The spectral irradiance between 290 nm and 400 nm is defined as 100 %.

### 4.3 Device for wetting the test panels

The test panels shall be wetted by condensation from the heated water tray and by spray. To prevent spotting on to the test panels, water with a pH value between 5,0 and 7,5 and an electrical conductivity of maximum 2 mS/m, measured at  $(25 \pm 1)$  °C shall be used. See Annex D.



#### 4.4 Black panel thermometer

Set the apparatus to operate at the specified parameters. The temperature shall be monitored by a remote sensor attached to the black panel. The black panel thermometer shall be exposed to the same exposure conditions as the specimens. Black panel thermometers shall be calibrated in accordance with the manufacturer's recommendations.

#### 4.5 Irradiance control

The irradiance at 340 nm shall be set to 0,89 W/(m<sup>2</sup>nm) (see 6.3.1).

Apparatus equipped with an irradiance control system shall be calibrated in accordance with the manufacturer's recommendations.

Lamps within the apparatus without an irradiance control system need to be rotated and replaced in accordance with the manufacturer's recommendations to compensate for lamp ageing.

### 5 Test panels

#### 5.1 Wood


The wood shall be Scots Pine (*Pinus sylvestris*) that has been selected free of knots, cracks and resinous streaks, to be straight-grained and of normal growth rate (i.e. 3 to 8 annual rings per 10 mm). The inclination of the growth rings to the face shall be 5° to 45° (see Figure 1).

The wood shall be free from blue stain and evidence of surface or bulk fungal infection. Abnormal porosity (caused by bacterial attack) shall be avoided (see Annex E).

武汉尚测试验设备有限公司

The panels shall be selected to give a sapwood test surface on the convex side of the growth rings, with no heartwood (if present), closer than 10 mm to the test surface. If the presence of heartwood in the selected pine cannot be detected by a difference in the colour in the wood, it shall be checked using the test described in Annex C.

The wood shall be conditioned at (20 ± 2) °C and a relative humidity of (65 ± 5) % (in accordance with ISO 554) to constant mass.

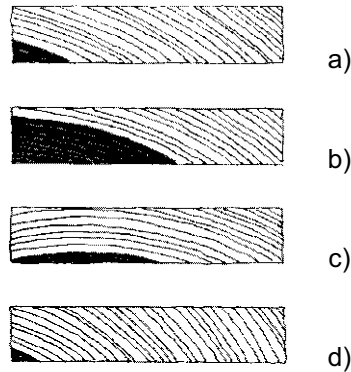

The topside of the panels is the exposed side, the bottom is the rear face

**Key**

- a) Example of a panel fulfilling the demands of growth ring orientation ( $5^{\circ}$  to  $45^{\circ}$ ) at the front side. No heartwood is closer than 10 mm to the test surface.
- b) This panel does not meet the specification because the heartwood is too close to the front side.
- c) This panel does not meet the specification because the growth ring orientation is not within the ( $5^{\circ}$  to  $45^{\circ}$ ) band. The growth rings incline at  $-10^{\circ}$  on the left of the panel and  $30^{\circ}$  on the right. Consequently a part of the surface contains a tangentially cut wood surface (growth ring inclination  $0^{\circ}$ ), with considerable risk of crack formation.
- d) This panel does not meet the specification because the growth ring orientation is not within the ( $5^{\circ}$  to  $45^{\circ}$ ) band and the growth rings incline  $45^{\circ}$  on the left of the panel and  $70^{\circ}$  on the right.

**Figure 1 — Cross section of panels**

**5.2 Preparation and selection of wood panels**

The panels shall be nominally  $(150 \pm 2)$  mm  $\times$   $(74 \pm 1)$  mm and  $(18 \pm 1)$  mm thick. The panels shall be planed to a smooth and uniform finish.

Any panels showing surface splitting shall be rejected. Where the presence of some minor defects in the test area are unavoidable, their position should be noted and their influence excluded during assessment of coating performance.

Mark the back of the panels to ensure that they can be identified during subsequent operations.

**5.3 Preparation of coated panels**

**5.3.1 Wood conditioning**

Prior to coating, condition the panels at  $(20 \pm 2)$  °C with a relative humidity of  $(65 \pm 5)$  % until the constant mass is in accordance with ISO 554. Keep the panels under the same conditions during drying of the coating system, and during subsequent storage of test panels before exposure. Panels may be transferred for brief periods to other ambient conditions where this is required for the conduct of specific operations or assessments.

**5.3.2 Preparation of panels for the test coating**

For each system select four panels from the available supply. Three panels shall be used for exposure and the fourth shall serve as an unexposed reference. In order to remove oleophilic films immediately before coating, the panels shall be hand sanded (mesh 150). Rounding of edges is not permitted.

Apply the coating system to all surfaces of each panel including end grain.

Apply the coating system using the method specified by the manufacturer to give a wet film thickness corresponding to the mean value ( $\pm 20\%$ ) of the manufacturer's recommended spreading rate.

Record the quantity of coating material applied to each test panel and subsequently calculate a mean value for the four panels. The values should preferably be stated in  $\text{g/m}^2$ , but may also be expressed as wet film thickness, in micrometres (see EN ISO 2808). The determination of the quantity of applied coating by weighing is the preferred method.

### 5.3.3 Conditioning

After the coating application age the panels for approximately 7 days in a controlled environment at  $(20 \pm 2)^\circ\text{C}$  and a relative humidity of  $(65 \pm 5)\%$  before carrying out the initial panels examinations.

## 6 Procedure

### 6.1 Examination before exposure

Before exposure carry out the following measurements:

- gloss;
- colour;
- dry film thickness (only reference panels);
- Adhesion (only reference panels).

As wood is a natural material, unexpected defects can be detected in the coated panels just before exposure, even though the wood material has been selected, inspected and prepared in keeping with the guidelines of 5.1 and 5.2. Exceptionally, if such panels are exposed, the type, size and position of the defects shall be noted so as to avoid any influence on the assessment after exposure.

For further details see annex A.

### 6.2 Mounting the test panels

Secure the test panels in the sample holders (whenever possible) with two exposure windows of approximately  $95\text{ mm} \times 64\text{ mm}$ . All spaces in the apparatus shall be occupied by test panels and any vacant spaces shall be occupied by blanks.

### 6.3 Exposure

#### 6.3.1 Exposure cycle

An exposure cycle of one week consists of a condensation period followed by a sub-cycle of water spray and UV-A 340 irradiation as given in Table 2.

**Table 2 — Exposure cycles**

Step	Function	Temperature	Duration	Condition
1	Condensation	(45 ± 3) °C	24 h	
2	Subcycle step 3 + 4		144 h consisting of 48 × cycles of 3 h consisting of steps 3 and 4	
3	UV	(60 ± 3) °C	2,5 h	irradiance set point 0,89 W/(m <sup>2</sup> nm) at 340 nm
4	Spray		0,5 h	6 l/min to 7 l/min, UV off

Rotate from middle to end, the sample position horizontally and vertically after each weekly cycle.

### 6.3.2 Sample rotation and maintenance

Once a week, examine the spray pattern using a glass cover in accordance with the manufacturer's recommendations and clean the spray nozzles if necessary.

### 6.3.3 Duration of test

The cycle lasts for 168 h (= 1 week). The cycle shall be repeated 12 times resulting in the total test exposure of 2016 h (= 12 weeks).

Testing the test panels shall be carried out without interruption except for servicing, maintenance of the apparatus and examination of the panels (see also B.5 relative to recommendation of periodical performance assessments).

## 6.4 Examination of test panels

At the end of the 12 week exposure period, examine the panels in accordance with Annex A. Remove the panels from the sample holder, assess blistering within 1 h and condition the panels for 7 days at a temperature of (20 ± 2) °C and a relative humidity of (65 ± 5) %.

Assess the panels for the following properties:

- flaking;
- cracking;
- chalking;
- gloss;
- colour;
- general appearance;
- adhesion.

For further details see annex A.

## 7 Precision

Precision data are not yet available.

## 8 Expression of results and test report

The test report shall contain at least the following information:

- a) all details necessary to identify the product tested, e.g. name and address of the manufacturer or supplier of the coating system tested, name or other identification marks of the coating system tested, including the batch number, description of the coating system tested;
- b) method and date of application, coating thickness and colour;
- c) reference to this Part of EN 927 (EN 927-6);
- d) name and address of the testing laboratory;
- e) type of apparatus used;
- f) identification number of the test report;
- g) name and address of the organization or the person who ordered the test;
- h) date and person responsible for the sampling;
- i) classification of the coating system in accordance with EN 927-1;
- j) date of receipt of the coating system tested;
- k) exposure period (start and finishing dates);
- l) method of colour measurement, i.e. 45/0 (specular component excluded) or  $d/8_{in}$  (specular component included); any deviations from the test methods specified;
- m) test results;
- n) authorization date of the test report.

## Annex A (normative) Details of test methods

### A.1 Gloss and change of gloss

Measure the specular gloss in accordance with EN ISO 2813 using a glossmeter at a 60° incident light angle. Obtain a minimum of two measurements on separate areas along the length of the panel, i.e. with the light beam parallel to the grain. Displace the glossmeter sideways and obtain a minimum of two measurements on adjacent areas with the light beam incident on the panel from the opposite direction. Take the mean of all measurements obtained.

Calculate the mean values for the change of gloss of the three exposed panels,  $CG_{ex}$ , and of the unexposed reference panel,  $CG_{ref}$ . Indicate the mean of the gloss with its standard deviation before and after weathering. Indicate the change of gloss and its standard deviation.

### A.2 Colour and colour change

Measure the colour in accordance with ISO 7724-2 using the measurement geometry 45/0 or d/8<sub>in</sub>. Determine the CIE 1976 colour co-ordinates ( $L^*a^*b^*$ ) for the standard illuminant D65 and standard observer 10° for each panel as a mean of a minimum four single measurements. In ISO 7724-1 and ISO 7724-2 the CIE 1964 (10°) standard observer and standard illuminant D65 shall preferably be used.

Calculate and state single measurements to one decimal place and the mean value and the standard deviation for all three panels to the nearest integer.

### A.3 Blistering

The assessment for quantity (density) shall be made separately on each exposed area in accordance with EN ISO 4628-2.

Calculate and record the mean value to one decimal place.

### A.4 Flaking

The assessment shall be made separately on each exposed area in accordance with EN ISO 4628-5, using a microscope of 10× magnification.

Calculate and record the mean value to one decimal place.

### A.5 Cracking

The assessment shall be made separately on each exposed area in accordance with EN ISO 4628-4.

Calculate and record the mean value to one decimal place.

### A.6 Chalking

The assessment shall be made separately on each exposed area in accordance with the procedure described in EN ISO 4628-6. Take care to distinguish between chalking and dust.

Calculate and record the mean value to one decimal place.

## A.7 General appearance

The general appearance is the visual impression of the tested coating system. It shall be rated on a scale as defined in EN ISO 4628-1:2003, Table 3, in comparison to the unexposed reference panels.

## A.8 Adhesion

### A.8.1 General

The assessment shall be made separately on each exposed area in accordance with EN ISO 2409.

### A.8.2 Apparatus and material

#### A.8.2.1 Cutting tool

Single-blade cutting tool with 20° to 30° edge and other dimensions as specified in EN ISO 2409 or a multi-blade cutting tool. The single-blade cutting tool is the preferred tool. The type of cutting tool used shall be stated in the test report.

#### A.8.2.2 Transparent pressure-sensitive adhesive tape

(25 ± 10) mm wide, with a minimum tensile strength of 200 N per 25 mm width and an adhesion of 6 N to 10 N per 25 mm width as specified in EN ISO 2409. The tape shall be stored at (20 ± 2) °C and a relative humidity of (65 ± 5) %.

### A.8.3 Procedure

The surface (and substrate) shall be clean and dry before the test.

Select an area free of blemishes and minor surface imperfections.

When cutting, use a ruler and cut through the coating down to the substrate in one steady motion.

Inspect the incisions to make sure that the film has been penetrated and the substrate is not unduly affected. If the incision is not satisfactory, make another one.

Remove two complete laps of tape from the roll and discard.

Smooth the tape into place at the area of the incisions and rub the tape firmly with a fingertip. The colour of the coating seen through the tape is a useful indication of overall contact. Within 5 min of applying the tape, remove it by seizing the free end pulling it off rapidly (but not jerking) back upon itself at an angle as close to 60° as possible.

Inspect the coated area for loss of coating; material attached to the tape shall be disregarded. Rate the adhesion in accordance with EN ISO 2409.

Perform the test twice on each exposed panel, recording individual results without decimals. Calculate and record the mean value for each panel to one decimal place. Calculate and state the mean value for all three panels to one decimal place.

## Annex B (informative) Explanatory notes

### B.1 Explanation of exposure cycle

The exposure cycle consists of a long initial condensation phase to generate moisture stress in the wood substrate, followed by rather short intervals of UV radiation and water spray to achieve a high number of short-term changes on the exposed surface. With this cycle the condensation is used to move moisture into the wood substrate while the water spray serves for the removal of degraded material from the sample surface and to produce frequent 'cold shocks'.

### B.2 Reproducibility

Possible sources for differences in the operation characteristics are:

- UV output of the fluorescent lamps (ageing). This effect can be minimised by the use of an automatic irradiance control system in all the devices.
- Level and/or fluctuations of the room climate with a possible influence on the effectiveness of the condensation and/or the spray water temperature.
- Water spray pattern and pressure (clogged spray nozzles) and water quality.
- Schedule of the sample rotation.

### B.3 Correlation to natural weathering

Bearing in mind the general limitations of an artificial test, the artificial weathering method appears suited to assess the performance of exterior wood coatings. However, the complicated interaction of a natural exposure cannot be completely simulated with a simple artificial exposure test.

The moisture content of the wood substrate during artificial weathering is still lower than during outdoor exposure. It is not clear whether this has an effect on the correlation of the test results.

### B.4 Dependency on wood species and substrate

Coating performance on pine panels should not be used to indicate performance on different wood species and substrates. Performance on other wood substrates would need to be evaluated.

### B.5 Recommendation of periodical performance assessments

Time-series types of data contain considerably more information than 'final' assessments only and are particularly useful in correlation studies. That is why periodical performance assessments are recommended during exposure for additional information on degradation process. Therefore, assessments could be made after 1, 2, 3, 4, 6, 10 and 12 cycles (for gloss after each cycle, see 6.4). In this case always make assessments at the end of the cycle (driest point of cycle). To avoid wetting of the samples before the assessment and to allow time for assessments, stop the cycle before the last step of spraying.



## **Annex C** (informative)

### **Test for heartwood in pine**

If the presence of heartwood in the selected pine cannot be detected by a difference in colour in the wood, it may be checked by the brush application of a test solution to both the end-grain and the faces of a small piece cut from the same length of timber.

Prepare this test solution by dissolving Fast Red B salt in de-ionized water at a concentration of 5 g/l. The solution should be freshly prepared and is immediately ready for use. Heartwood is indicated by the development of a deep red colour, which usually shows within about 10 min.

**NOTE** Fast Red B has no reported mutagenic or teratogenic effects, however, it should be treated as a suspected carcinogen. Reference should be made to up-to-date, relevant health and safety data sheets.

## **Annex D** (informative) **Water treatment, devices for water purification**

Water of the required quality can be produced with a mixed bed deionizing system with a Type 1 anion exchanger (not Type 2), or with a combination of reverse osmosis and deionization.

Distilled or deionized water of the required quality in a tank with a continuous conductivity measurement has been found suitable. A recirculation system including a pump and filters provides the water for spraying onto the test panels and also keeps it free from contamination. The conductivity meter indicates polluted water ( $> 2$  mS/m) and therefore the time to renew the water. Weekly exchange of the water has been found sufficient.

Distilled water from heating systems can be used provided the plumbing can be shown not to contaminate the water.

**Annex E**  
(normative)  
**Test for abnormally porous wood**

Abnormally porous wood may be detected qualitatively by the rapid absorption of a drop of propan-2-ol (isopropanol) applied to a small surface; the drop should not be absorbed in less than 30 s by normal wood. The test should be carried out at not less than six places, widely separated on the test panel.

Carry out the test on the backside of the panel.

## **Annex F** (informative) **Alternative procedure for preparation and coating of panels**

An alternative preparation of test panels may be used, e.g. for industrially applied coating systems. In this case prepare larger panels first, plane their surfaces, apply and dry the coating system (including conditioning), cut the final panel size (see 5.2) and seal the end grain and edges of the panel with at least two coats of the product under test or a flexible, moisture-impermeable paint, for example of long-oil alkyd type.

## Bibliography

- [1] EN 927-3, *Paints and varnishes — Coating materials and coating systems for exterior wood — Part 3: Natural weathering test*
- [2] EN ISO 2810, *Paints and varnishes — Natural weathering of coatings -- Exposure and assessment (ISO 2810:2004)*
- [3] EN ISO 4892-1, *Plastics — Methods of exposure to laboratory light sources — Part 1: General guidance (ISO 4892-1:1999)*
- [4] EN ISO 4892-3, *Plastics — Methods of exposure to laboratory light sources — Part 3: Fluorescent UV lamps (ISO 4892-3:2006)*
- [5] ASTM G151, *Standard Practice for Exposing Nonmetallic Materials in Accelerated Test Devices that Use Laboratory Light Sources*
- [6] ASTM G154, *Standard Practice for Operating Fluorescent Light Apparatus for UV Exposure of Nonmetallic Materials*

---

## BSI - British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001 Email: [orders@bsigroup.com](mailto:orders@bsigroup.com) You may also buy directly using a debit/credit card from the BSI Shop on the Website <http://www.bsigroup.com/shop>

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact Information Centre. Tel: +44 (0)20 8996 7111 Fax: +44 (0)20 8996 7048 Email: [info@bsigroup.com](mailto:info@bsigroup.com)

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002 Fax: +44 (0)20 8996 7001 Email: [membership@bsigroup.com](mailto:membership@bsigroup.com)

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsigroup.com/BSOL>

Further information about BSI is available on the BSI website at <http://www.bsigroup.com>.

### Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright and Licensing Manager. Tel: +44 (0)20 8996 7070 Email: [copyright@bsigroup.com](mailto:copyright@bsigroup.com)